



PRODUCT DESCRIPTION

ACRYNAR FX extrusion coatings are two-coat systems consisting of a patented primer and a durable color coat, available in a wide range of solid colors and mica pearlescent flakes. ACRYNAR FX durable spray coatings offer building architects and specifiers unique blend of properties which approach the performance of a superior performing AAMA 2605-type coating. They combine PPG proprietary resin and pigment technologies with ultra durable fluoropolymer resin. The result is an AAMA 2604-compliant finish with long-term durability and excellent aesthetics.

SYSTEM OVERVIEW

ACRYNAR FX durable spray coatings represent a new level of performance for architectural applications. They have the proven painter-friendly application properties that have made DURANAR® coatings so popular over the past 30 years. This two-coat system can be applied “wet-on-wet” with

nominal coating thickness of 0.2 mil primer and 1.0 mil topcoat. Film hardnesses of H-2H can be achieved with ACRYNAR FX. ACRYNAR FX coatings offer excellent aesthetics. The proprietary resin technology formulated into these coatings produces hard, yet smooth finishes.


COMMERCIAL USES

Architects and specifiers want coatings that provide an attractive appearance throughout a building’s lifetime. ACRYNAR FX coatings’ combination of improved mar resistance and excellent weatherability make them an intelligent choice for use in high traffic areas such as store fronts, schools, hospitals, and high-rise condominiums. It should be

noted that ACRYNAR FX coatings are not a replacement for PPG DURANAR fluoropolymer coatings which meet the performance requirements of the AAMA 2605 specification. DURANAR coatings are the architectural coatings of choice when ultimate durability and performance are specified.

DURABILITY

ACRYNAR FX coatings meet the AAMA 2604 weathering specifications of less than 5ΔE units color fade, maximum chalk rating of 8, and greater than 30% gloss retention after five years of exposure in south Florida. For projects requiring easy-to-apply finishes that are mar resistant and offer improved long-term durability, ACRYNAR FX durable spray coatings are the best choice.

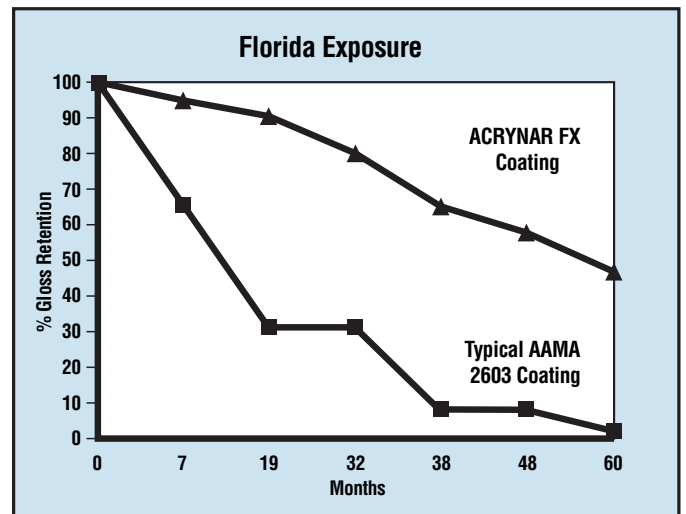

Five-Year Florida Weathering Data Comparison



ACRYNAR FX SPECIFICATIONS	
Colors Available	White, black, and a wide range of solid colors including micas
Dry Film Thickness ASTM D1400	0.2 mil min. primer 1.0 mil min. color coat
Gloss ASTM D523 @ 60°	Low and medium
Pencil Hardness ASTM D3363	F minimum
Cross Hatch Adhesion 1/16" wet and dry	No removal
Direct Impact 1/10" distortion	No removal
Abrasion - Sand Falling ASTM D968	40 l/mil
Acid Resistance ASTM D1308 10% muriatic acid spot test	15 minutes – No attack
Alkali Resistance Mortar pat test 100% relative humidity @ 100°F	24 hours – No attack
Detergent Resistance 3% immersion @ 100°F	72 hours – No attack
Salt Spray Resistance ASTM B117, 3000 hrs. 5% NaCl @ 95°F	1/16" max. undercutting
Humidity Resistance ASTM D714 ASTM D2247, 3000 hrs. 100% relative humidity @ 100°F	Few #8 blisters.
Exterior Exposure 5 yrs. @ 45, south Florida ASTM D2244 ASTM D4214 Film Integrity Gloss Retention	Max. 5 fade Max. 8 chalk Very good Greater than 30%

ACRYNAR FX WARRANTY INFORMATION

PPG offers a comprehensive warranty on ACRYNAR FX extrusion coatings. For complete warranty information and a copy of the ACRYNAR FX extrusion coatings warranty, please call PPG at **1-800-258-6398**.

